



# Exterior Decorative Coatings Improvements on Commercial Airplanes

by  
Elden Altizer\*  
Material & Processes Technology  
Boeing Commercial Airplanes,  
Seattle, WA, USA

**Commercial aviation is a highly competitive industry for both the OEM (Original Equipment Manufacturer) and the airlines. The exterior coatings on airplanes are increasingly being used for branding and marketing by the airlines, in addition to the protective function they must provide the airframe from extreme environmental conditions. This paper covers the fundamental environmental and performance requirements of the exterior decorative coating system, the processes and materials used to paint these airplanes, current improvements and future goals. Special emphasis will be given to investigation and solution to the paint adhesion issue known in aerospace as "rivet rash."**

Commercial aerospace is a truly worldwide industry that has evolved into a duopoly of Boeing and Airbus for the supply of large aircraft to an increasingly complex market on the airline side. For the airlines, the effects of the deregulation that began in the 1980s, and continuing with this year's Open Skies agreement for Europe and North America, has caused a major shift in the economics of the airline industry. In this market driven by low fares and low operating costs, branding has played an increasing role in airline's efforts to attract and keep customers. The most striking way to differentiate an airline's image is the exterior decorative paint.

The exterior coatings perform both a decorative and protective role. This paper will focus on the Boeing system for aluminum airplanes, where the corrosion protection begins with clad aluminum. This clad finish provides a primary level of corrosion protection that allows for an unpainted finish such as that used by American Airlines.

For painted exterior designs, called the livery, the following process steps are performed. It is noteworthy that all of the preparation and painting of the airplane is a manual process. The exterior aluminum

clad skins are received in the paint hangar with an alkaline removable temporary protective coating (TPC). The TPC is removed with a thickened alkaline cleaning solution and rinsed with copious amounts of water. The next step is to clean the surface with a combination of solvent and alkaline cleaners to remove any residual protective coating and other contaminants that end up on the skin from upstream manufacturing processes, such as drilling lubrication or sealant splatters. Once the skin is chemically clean, a de-oxidation step is performed by either manually wet power abrading with abrasive pads or by applying an acid cleaner. This is followed by application of a conversion coating to enhance the adhesion of the primer. A solvent borne corrosion-inhibiting epoxy primer is then followed by a polyurethane topcoat.

This basic process has been used since the 1960s. While there had been some incremental changes in the process through the 70s and 80s, the most dramatic driver for change came with the creation of Aerospace specific environmental regulations in the United States. The Aerospace National Emission Standards for Hazardous Air Pollutants (ANESHAP) were implemented in September 1998.

---

\* Corresponding author:  
Mr. Elden Altizer  
Material & Process Technology  
The Boeing Company  
M/C 0F-45  
Seattle, WA 98124  
Phone : (425) 260-0575  
E-mail: elden.l.altizer@boeing.com



Figure 1—Severe “rivet rash” by flight deck window.

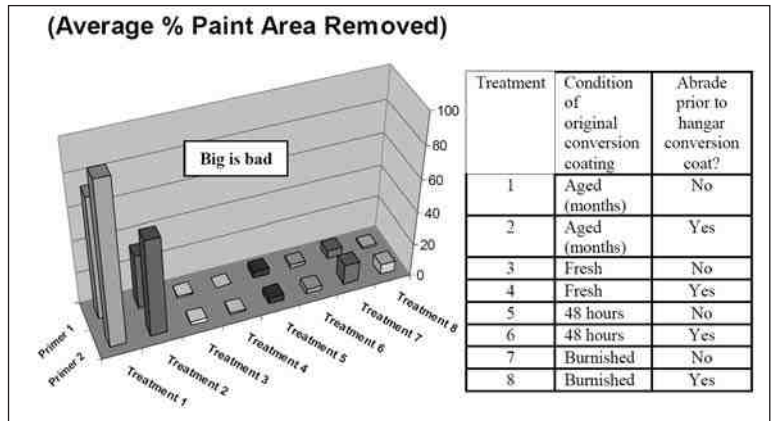


Figure 2—The adhesion of primers based on the surface treatment following the rivet manufacturing processes.

These regulations included changes in solvent cleaning, spray gun cleaning, paint stripping and the use of low VOC (Volatile Organic Compound) primers and topcoats. The ANESHAP regulations required primers and topcoats to meet VOC limits of 350 and 420 grams VOC/liter, respectively.

### Performance and environmental requirements

Corrosion and substrate protection are the fundamental roles of finishes on airplanes. For Boeing airplanes, the primary corrosion protection for the exterior fuselage is the aluminum cladding bonded to the surface of the particular alloy. The corrosion protection provided by this thin layer of cladding is why Boeing airplanes can remain unpainted (polished). However protective coating is always required for composite structures to protect the resin from UV degradation. Coated metal parts require a corrosion inhibiting primer that contains hexavalent chromium.

The coatings on the exterior must withstand one of the most demanding environments of any coating. The finish is subjected to thousands of thermal cycles ranging from +160° to -60°F, intense UV exposure at high altitudes, aerodynamic and erosion forces up to 600 mph, and contact with fuel, oils and hydraulic fluid. The phosphate ester fire resistant hydraulic fluids are particularly aggressive and would cause automotive topcoats to bubble in less than a day, yet the aerospace finish system is expected to last up to eight years, depending on each airline's maintenance schedule.

### Rivet rash

The selective loss of paint adhesion on aluminum rivets, shown in Figure 1, is known in the aerospace industry as “rivet rash.” This condition has existed to varying degrees since the beginning of the jet aircraft age. It is such a common condition that there is a good chance that every reader has boarded an airplane with rivet rash and never given it a thought. But rivet rash started to appear earlier and more severe after the change to ANESHAP\*\* compliant coatings.

Customer feedback and fleet surveys prompted Boeing to initiate an investigation to understand more fully the root cause of the rivet rash. The study focused on the primer adhesion to the fasteners in comparison to the clad aluminum skin. Boeing investigated not only the paint hangar processes, but also the rivet manufacturing process and the mechanical, chemical and aging life cycle of the rivets prior to reaching the paint hangar.

This investigation was quite extensive and this paper will not cover the details of that effort. However, the key finding of this investigation was that the conversion coat applied to the raw rivets at the manufacturer became detrimental to adhesion of primer as it aged. Figure 2 shows the impact of primer adhesion on aged and fresh conversion coated rivets and alternative finishing processes (burnishing and abrading of the rivet head only to remove the conversion coat).

While an obvious conclusion would be not to apply the conversion coating at the rivet manufacturer, issues surrounding compatibility with multiple specifications, both military and commercial users, supply chain processes and other factors made this unfeasible.

A solution that avoided most of the issues above was the addition of an extra conversion coating to promote adhesion. Boeing and our rivet manufacturer\*\*\* developed a process that added a sol-gel coating to the rivets while the initial conversion coating was not aged.

Rivets were installed in test foils for the Boeing Whirling Arm Rain Erosion test, which subjects foils to simulated rain at high speed. A decorative paint system was applied to the foils and the adhesion to the rivets was noted. Figures 3 and 4 show a dramatic improvement in adhesion provided by the sol-gel coating.



Figure 3—Standard rivet finish.



Figure 4—Sol-gel rivet finish.

\*\* Aerospace National Emission Standard for Hazardous Air Pollutants

\*\*\* Allfast Fastening Systems, City of Industry, CA 91745.

Treatment	Abrade?	Solvent?	Acid Clean?	Conversion Coating Type?
1	No	No	No	Type 1
2	Yes	No	No	Type 1
3	No	Yes	No	Type 1
4	No	No	Yes	Type 1
5	No	No	Yes	Type 1
6	No	No	No	Type 2
7	Yes	No	No	Type 2

Figure 5—Sample of rivet head surface treatments prior to priming.

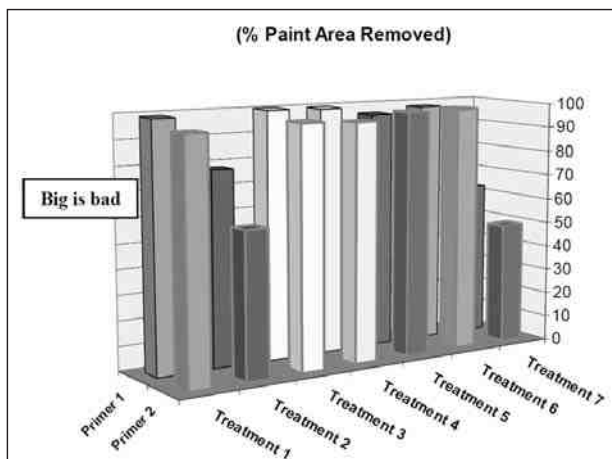


Figure 6—The effect of the standard aged rivet finish as painted in production.

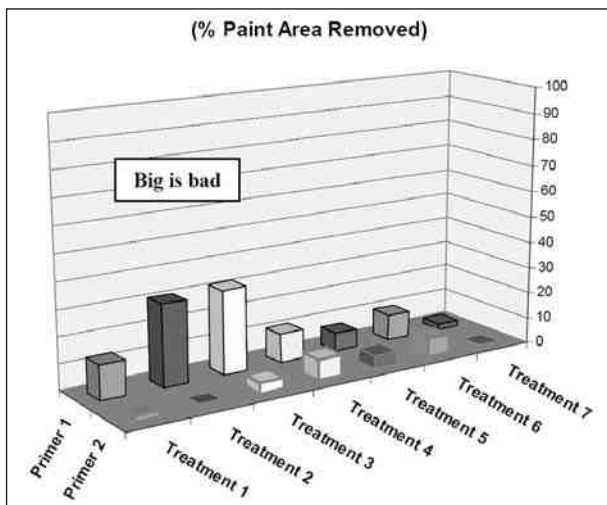


Figure 7—The effect of the rivet new sol-gel finish as painted in production.



Figure 9—Rivet rash on a Boeing 777 painted prior to sol-gel rivet conversion after 18 months in-service.

The benefit of the sol-gel technology for promoting primer adhesion on rivets that are prepared with different cleaning processes (defined in Fig. 5) and primers are shown in Figs. 6 and 7.

The new sol-gel finish was implemented in early 2003 on all aluminum fasteners produced by Allfast, the sole supplier to Boeing and our parts suppliers. Since the clear sol-gel coated rivets are not visibly different from the non-sol-gel, the main tool to identify them is by the packing as shown in Fig. 8.



Figure 8—Standard one pound bag of aluminum rivets with sol-gel noted on packaging.

Given the large number of suppliers and parts that receive rivets, Boeing focused the initial use of the sol-gel coated rivets on the high erosion front section of the fuselage, known as the 41 section, where the occurrence of rivet rash is most severe. By 2004 the conversion of the 41 section to all sol-gel coated rivets was complete for all Boeing models.

#### Plan – Act – Assess: Verifying the results

The year following the implementation of the new rivet coating, Boeing surveyed the performance on various models operating in Europe, Asia and North America. The results were encouraging as the onset and occurrence of rivet rash was significantly lower than prior to the sol-gel coating, but it was not completely eliminated (see Figs. 9 and 10).



Figure 10—Minimal rivet rash on a Boeing 777 painted after sol-gel rivet conversion after 14 months in-service.

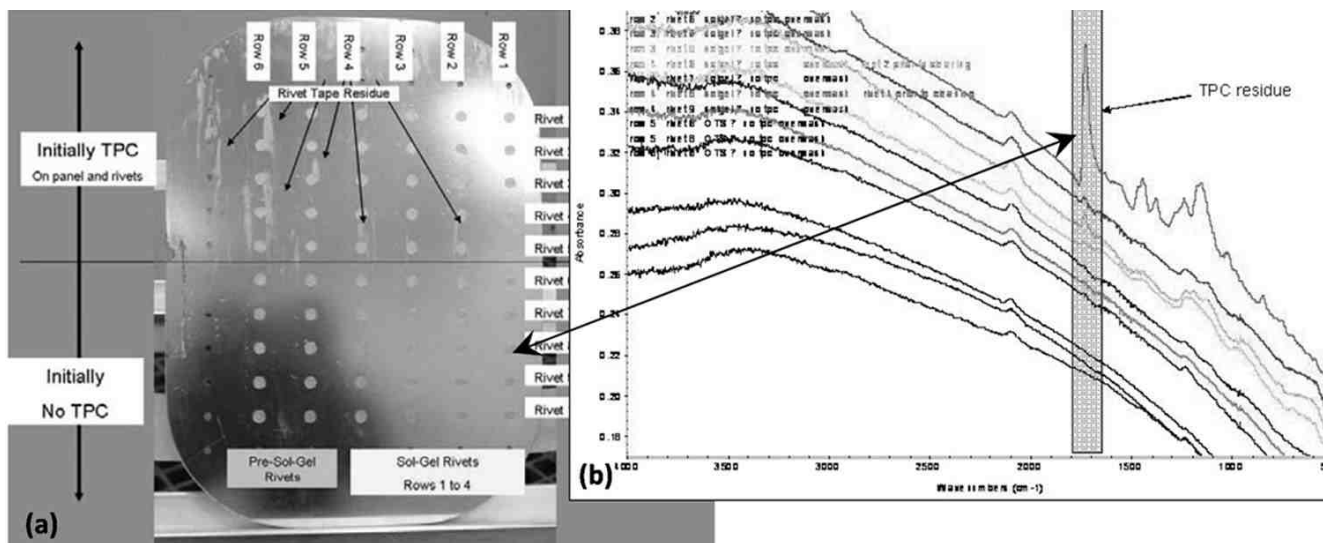


Figure 11—(a) FT/IR showing TPC residue; (b) riveted test panel evaluating the impact of TPC residue.

Further laboratory testing found that sol-gel coated rivets made in-process contamination a significant issue. Testing the new sol-gel coated rivets in skin panel cutouts revealed the TPC removal process allowed TPC residue to be deposited on the rivet surface and interfere with the primer adhesion. The properties of sol-gel that promoted adhesion with the primer also bonded well with the TPC resin. A test carried out to verify the impact of TPC contamination is presented in Figs. 11a and b.

The in-service data showed a negative impact on the 41 section only. The areas aft of the high erosion zone remained free of rivet rash based on the most recent survey data. To address the high erosion areas, Boeing added an additional manual abrasion cleaning step to the surface preparation on section 41.

### Closing the gap on adhesion loss: primers and conversion coating

While the additional abrasion cleaning process provided the adhesion improvement for the airlines, we were concerned about the negative ergonomic impact on our workforce, as well as the inherent variability of a manual process. In 2005, independent projects, on primer and conversion coating, began yielding results that could further improve the adhesion of the exterior coatings.

The primer project found high solids primers from our two decorative coatings suppliers appeared to offer higher adhesion values than the currently used high solids primer. Scale-up of the primers progressed to a point that production trial airplanes were successfully painted in early 2006. Both these primers were added to the exterior paint specification and production was

converted to these primers by mid-2007. A recent inspection of one of the airplanes, after over 4,000 flight hours, found no paint loss on any rivets.

In 2006, Boeing also tested two non-chromated conversion coatings, one of which was a commercialized version of the Boeing patented sol-gel. While both conversion coats met the environmental chromium reduction goals, the sol-gel product, when tested for rivet adhesion, produced superior paint adhesion when compared to the other non-chromium conversion coat. A full scale test was performed on a flight test airplane for the Boeing 777-200LR program. Two airplanes were part of the flight test program, so the conventional

chromated conversion coating was used on one airplane and the sol-gel product on the second. After almost a year in test, the sol-gel treated airplane had no rivet rash, while the conventional coating showed 11 rivets with adhesion loss.

The full scale airplane test also provided an additional important test with the chemical stripping required prior to repainting the airplane in the airline customer's livery. The paint applied to sol-gel conversion coat, while requiring slightly more time to strip, was completely and successfully removed with a peroxide activated, benzyl alcohol paint stripper commonly used today for environmental compliance (see Fig. 12).

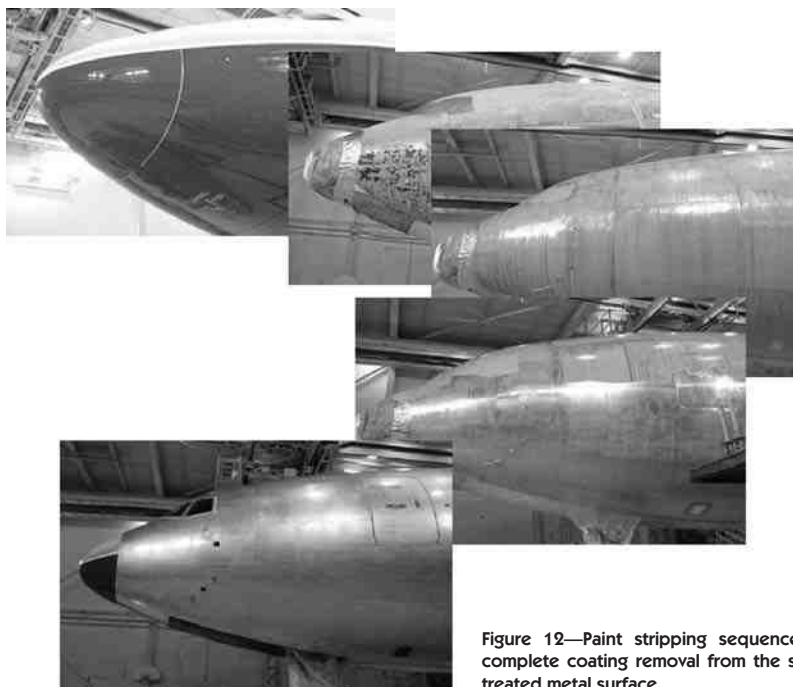


Figure 12—Paint stripping sequence and complete coating removal from the sol-gel treated metal surface.



## Conclusions and future directions

The performance of these improvements will not be fully known until after two to three years of in-service operation, although the initial results are very encouraging. Airlines are already experiencing a significant reduction in rivet rash and the improvements implemented in 2007 should complete the efforts to eliminate rivet rash. The knowledge gained by this effort has been incorporated into the requirements for future material evaluation.

In addition, new material evaluations continue. At the top of the priority list are new materials that make all our processes more robust and stable, as well as efforts to eliminate chromium from our primers and other environmental improvements. Almost every paint hangar process has an improvement effort at the idea stage, completing feasibility or ready to implement. On top of all these projects on existing models, the era of the all composite airplane, the Boeing 787, is about to begin.

But that's another story.

The author wishes to acknowledge the contributions and efforts of the following Boeing engineers and technicians to this effort: Randy L. Jähren, Kay Y. Blohowiak, Ronald Wu, Mark P. Johnson, Craig Ungerecht, Dara Ung, Grant Ripley, Paul J. Ambrose and Bud Jewett. *P&SF*



## 2008—SAVE THE DATES!

### 2008 NASF Washington Forum

April 22-24, 2008

L'Enfant Plaza Hotel • Washington DC

\* The Washington Forum is a two-day event packed with top speakers and panel discussion followed by visits to Capitol Hill.

### SUR/FIN 2008

June 16-18, 2008

Indiana Convention Center • Indianapolis, IN

\* SUR/FIN is the premier industry conference and trade show. This major international conference provides the best venue to explore the newest technology, showcase products and services and network with thousands of people involved in the surface finishing industry.

More information on-line: [www.nasf.org](http://www.nasf.org)




Attention Job Shops and Suppliers

## SFMRB METAL FINISHING INDUSTRY MARKET SURVEY

### Report No. 10

Surveying NAFTA Market Trends

*Includes data from the world's major metal finishing chemical suppliers and the largest North American job shop platers.*

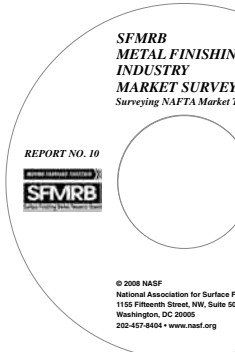

**Both the NAFTA and worldwide electroplating markets continue to change. To obtain better current information, NASF conducted the 10th SFMRB (Surface Finishing Market Research Board) survey since 1995.**

The purpose of this survey is to define the current size of the NAFTA metal finishing chemical and electroplating services markets and will include data from the world's major metal finishing chemical suppliers and the largest North American job shop platers. Information will be reported on the size of the various North American plater markets and employment, trends of plating processes and user markets, the major challenges facing the industry and much more.

*\* If your company submitted data for the survey you will receive \$50 off the price*

Name \_\_\_\_\_

Company \_\_\_\_\_

Address \_\_\_\_\_

\_\_\_\_ Member: \$350    \_\_\_\_ Non-Member: \$1500

### Billing Information

Check enclosed for \$ \_\_\_\_\_

(Please make checks payable to NASF.)

*Funds must be in U.S. currency drawn on a U.S. bank or credit cards only.)*

Type of Card: ☐ American Express ☐ MasterCard ☐ VISA

Credit Card Number: \_\_\_\_\_

Expiration Date: \_\_\_\_\_

Name on card: \_\_\_\_\_

Card Billing Address: \_\_\_\_\_

Signature \_\_\_\_\_



NASF, 1155 Fifteenth St., NW, Suite 500,  
Washington, DC 20005; Tel.: 202-457-8404  
FAX: 202-530-0659